

Prijava naučnog rada

Podaci o radu:

Rad ¹	Determination of Internal Pressure Value Causing Pipe Branch Model to Plastically Deform
ISSN časopisa	1451-2092
Impakt faktor časopisa ²	0,59 (SCOPUS)
Datum objavljivanja rada	2018
Naziv liste kojoj časopis pripada	Emerging Sources Citation Index (ESCI) SCOPUS
Ukupan broj autora	5
Broj autora koji nisu zaposleni na UCG	4
Naziv vodećeg autora	Prof.dr Taško Maneski

Autori rada:

R.B.	Ime i prezime autora zaposlenih na organizacionoj jedinici
1	Prof.dr Darko Bajić, Mašinski fakultet
2	
3	
4	
5	

Datum podnošenja prijave:

16.03.2018.

Podnosioci prijave:

1. prof.dr Darko Bajić
(Ime i prezime autora)
2. _____
(Ime i prezime autora)
3. _____
(Ime i prezime autora)
4. _____
(Ime i prezime autora)
5. _____
(Ime i prezime autora)

¹ Puna referenca rada

² Ne smije biti stariji od 2015. godine



UDC: 621

ISSN 1451-2092

University of Belgrade
Faculty of Mechanical Engineering

FME TRANSACTIONS

New Series, Volume 46, Number 2, 2018

Editor:

Boško Rašuo
University of Belgrade

Associate Editor:

Stevanović Vladimir
University of Belgrade

Editorial Board:

Avellan François
Swiss Federal Institute of Technology, Zurich, Switzerland

Cizmas Paul
Texas A&M University, College Station, USA

Dulikravich S. George
Florida International University, Miami, USA

Đorđević Vladan
University of Belgrade

Ehmann F. Kornel
Northwestern University, Evanston IL, USA

Felix Hong
Wayne State University, Detroit, USA

Gabi Martin
Karlsruher Institut für Technologie (KIT), Germany

Gajić Zoran
Rutgers University, USA

Jakirlic Suad
Technische Universität Darmstadt, Germany

Jovanović Jasmina
University of Belgrade

Kartnig Georg
Technische Universität Wien, Austria

Klimenko A. Sergei
National Academy of Sciences, Kiev, Ukraine

Komatina Mirko
University of Belgrade

Meerkamm Harald
Friedrich-Alexander-Universität Erlangen-Nürnberg, Germany

Mester Gyula
University of Szeged, Szeged, Hungary

Minak Giangiacomo
Alma Mater Studiorum - University of Bologna, Italy

Nedić Novak
University of Kragujevac

Plančak Miroslav
University of Novi Sad

Putnik Goran
University of Minho, Portugal

Radovanović Miroslav
University of Nis

Sedmak Aleksandar
University of Belgrade

Soutis Constantin
The University of Manchester, Manchester, UK

Stamenović Dimitrije
Boston University, Boston, USA

Technical Editor:

Sedmak Simon
University of Belgrade

Published by:
University of Belgrade
Faculty of Mechanical Engineering

The journal is covered in the Emerging Sources Citation Index (ESCI) Clarivate Analytics services.

Volume 46, No 2, 2018, pp. 151 – 290

CONTENTS

	PAGE
Claudir Gabriel Kaufmann Jr, Rúbia Young Sun Zampiva, Carlos Pérez Bergmann, Annelise Kopp Alves, Sergio Roberto Mortari, Ana Pavlovic <i>Production of Multi-wall Carbon Nanotubes Starting from a Commercial Graphite Pencil using an Electric Arc Discharge in Aqueous Medium</i>	151
Rúbia Young Sun Zampiva, Claudir Gabriel Kaufmann Jr, Annelise Kopp Alves, Carlos Pérez Bergmann <i>Influence of the Fuel Composition and the Fuel/Oxidizer Ratio on the Combustion Solution Synthesis of MgFe₂O₄ Catalyst Nanoparticles</i>	157
Purnomo, M. Subri, P. Setyarini <i>Fracture Development and Deformation Behavior of Zeolite-Filled High Density Polyethylene Annealed Composites in the Plane Stress Fracture</i>	165
W.A. Waleed, A. Chathriyan, R. Sam Singh Vimal <i>Experimental Investigation On the Influence Of Process Parameters In Thermal Drilling Of Metal Matrix Composites</i>	171
V. Dovhaliuk, O. Gumen, V. Mileikovskiy, V. Dziubenko <i>Simplified Analysis of Turbulence Intensity in Curvilinear Wall Jets</i>	177
Vladimir S. Poluzanski, Uros D. Kovacevic, Bosko D. Nikolic <i>Algorithm for Calculating Influence of Power Transformer Oil Temperature Change on the Accuracy of All-Acoustic Non-Iterative Partial Discharge Localization</i>	183
Edward E. Osakue, Lucky Anetor <i>Design of Straight Bevel Gear for Pitting Resistance</i>	194
Davood Khoeini, Mohammad Reza Tavakoli <i>The Optimum Position of Impeller Splitter Blades of a Centrifugal Pump Equipped with Vaned Diffuser</i>	205
Péter Böröcz <i>Averaged Vibration Levels During Courier Parcel Delivery Service in Small Truck in Hungary</i>	211
Taško Maneski, Darko Bajić, Nikola Momčilović, Vesna Milošević Mitić, Martina Balać <i>Determination of Internal Pressure Value Causing Pipe Branch Model to Plastically Deform</i>	218
A. Saboktakin, T. Vu-Khanh, V. Butun, P. Pantyukhov <i>Characteristics of Tufted Preforms Subjected to Different Mechanical Loading for Aerospace Applications</i>	224
S. Sadeghi, N. Zarif Karimi, M. Fotouhi, M. Hasani, M. Ahmadi Najafabadi, A. Pavlovic <i>Residual Stress Evaluation in Friction Stir Welding of Aluminum Plates by Means of Acoustic Emission and Ultrasonic Waves</i>	230
Mohamad Fotouhi, Putu Suwarta, Meisam Jalalvand, Gergely Czél, Michael R. Wisnom <i>Acoustic Emission Monitoring of Thin Ply Hybrid Composites under Repeated Quasi-Static Tensile Loading</i>	238

(Contents continued on inside back cover)

The publication of the Vol. 46, No 2 of this Journal was fully financially supported by the Ministry of Education and Science of the Republic of Serbia. This support is gratefully acknowledged.

Printed by:
"PLANETA print", Ruzveltova 10, 11000 Belgrade

Aims and Scope:

The journal FME Transactions publishes original papers (reviewing and contributed papers, and short communications) from all fields of Mechanical Engineering, which is, as a branch of Engineering, considered in the journal in its broadest possible sense. Thus, the articles are welcome from: Applied Mechanics, Fluids Engineering, Thermodynamics, Heat and Mass Transfer, Robotics, Material Science, Tribology, Combustion, Mechanical Design and Machine Dynamics, Productional, Industrial, Agricultural, Aerospace, Processing, Railway, Biomedical and Control Engineering, Mechanization, Hydro- and Thermo-power Systems, Internal Combustion Engines and Vehicle Dynamics, Energy Resources Technology, Military Technology, Naval Architecture, and Applied and Industrial Mathematics.

Theoretical, experimental and computational analyses of various problems of Mechanical Engineering are equally welcome and acceptable for publication. In addition, there will be published book reviews, announcements of symposia, and in special issues, proceedings of selected papers from symposia organized by the Faculty of Mechanical Engineering in Belgrade.

Reviewing papers will be published by invitation only. One volume consists of four numbers.

Instructions for Authors:

A FME Transaction manuscript should be written clearly and concisely in correct English, with assumptions clearly identified, with precise logic, with relevance to practice described, and with actual accomplishments of the work plainly stated and honestly appraised.

Normally, the length of a reviewing paper is up to 12 pages, the length of a contributed paper is up to 8 pages, while the length of a short communication should not exceed 4 pages. All papers are subject to a reviewing process. During the process the names of referees will be kept confidential to authors, and also the names of authors will remain anonymous to referees. As a rule the reviewing process should be accomplished in 2-3 months. Final acceptance of a paper for publication in the Journal is based on the decision of the Editorial Board.

Template for Manuscript:

<http://www.mas.bg.ac.rs/transactions>

Submission of Papers:

Papers intended for publication in FME Transactions should be submitted to the Editor, in the electronic form, to the following address:

fme-transactions@mas.bg.ac.rs

or:

Prof. Bosko Rasuo, Editor
brasuo@mas.bg.ac.rs
Faculty of Mechanical Engineering
Kraljice Marije 16,
11120 Belgrade 35
Serbia

On line service:

<http://www.mas.bg.ac.rs/transactions>

ISSN 1451-2092

UDC: 621

Volume 46, No 2, 2018, pp. 151 – 290

CONTENTS CONTINUED

	PAGE
J. Yousefi, A. Mahdian, N. Zarif Karimi, H. Heidary, M. Ahmadi, G. Minak	245
<i>Damage Analysis for Low Velocity Impacted Composite Laminates using Acoustic Emission Technique</i>	
C. Mahil Loo Christopher, T. Sasikumar, C. Santulli, C. Fragassa	253
<i>Neural Network Prediction of Aluminum–Silicon Carbide Tensile Strength from Acoustic Emission Rise Angle Data</i>	
Mauricio Knak de Almeida, Ênio Leandro Machado, Diosnel Antonio R. Lopez, Pâmela Andréa M. dos Santos, Carlos Pérez Bergmann, Adriane de Assis L. Rodriguez	259
<i>Synthesis of TiO₂-based Photocatalysts and their Use in the Degradation of the Semi-precious-gemstone-coloring Dye Rhodamine B</i>	
Dušan Č. Šarac, Nenad R. Mitrović, Ivan V. Tanasić, Ljiljana Tihaček-Šojić	266
<i>Experimental Methodology for Analysis of Influence of Dental Implant Design on Load Transfer</i>	
Redouane Assoudi, Khalid Lamzoud, Mohamed Chaoui	272
<i>Influence of the Wall Roughness on a Linear Shear Flow</i>	
Borut Jereb, Samo Kumperščak, Tadej Bratina	278
<i>The Impact of Traffic Flow on Fuel Consumption Increase in the Urban Environment</i>	
Damir Belic, Zoran Kunica, Tihomir Opetuk, Goran Dukic	285
<i>Optimization of the Plant Layout in the Production of the Special Transformers - Case Study</i>	

Determination of Internal Pressure Value Causing Pipe Branch Model to Plastically Deform

Taško Maneski

Full Professor
University of Belgrade
Faculty of Mechanical Engineering

Darko Bajić

Professor
University of Montenegro
Faculty of Mechanical Engineering
Montenegro

Nikola Momčilović

Assistant Professor
University of Belgrade
Faculty of Mechanical Engineering

Vesna Milošević Mitić

Full Professor
University of Belgrade
Faculty of Mechanical Engineering

Martina Balać

Research Associate
University of Belgrade
Faculty of Mechanical Engineering

Complexity of pressure vessels geometry usually causes stress and strain concentrations. Modern approach of stress and strain analysis involves numerical and experimental testing. Every experimental testing on the construction could endanger construction itself. Therefore, making a model of the construction has great benefits. Sub-sized model of the pipe branch of A6 third pipeline at Hydropower Plant Perućica, Nikšić was made in order to be subjected to a detailed experimental testing. The aim was to determine internal pressure value causing pipe branch model to plastically deform, and, to use these results for determining pressure causing real structure to plastically deform, without any measurements on the structure itself. Experimental measurements were carried out using strain gauge method. Strain gauges are positioned in critical zones. Numerical pipe branch model and results obtained by using finite element method (FEM) was verified with experimental results (in elasticity area). After verification in elastic area, experimentally by increasing pressure value, critical internal pressure causing plastic deformation of pipe branch model was determined. Based on the pipe branch model behaviour, and after determination of relation between the model and the real structure, maximum calculated internal pressure value to which the structure may be subjected in exploitation is assessed. Besides, weak spots on the structure were verified by obtaining the same results through experiment and calculation, which gives good guidelines for monitoring of this structure during usage, since it is possible, by using this analysis, to decrease the number of measurement locations for monitoring (in order to control exactly those measurement locations, which proved to be the most endangered).

Keywords: pipe branch model, plastic deformation, finite element method, strain gauges, stress

1. INTRODUCTION

Pressure vessels besides internal pressure load, may be subjected to temperature and mechanical loads [1,2]. This induces internal stresses causing failure of the structure. Stress change analysis in the vicinity of a location where two or more shells of different geometrical shapes intersect or join represents a problem many researchers deal with. Engineering way of determining stress distribution of pressure equipment subjected to different load types (internal pressure, external forces, moments) uses methods resulting from theoretical or experimental researches [3-7]. In papers [4,5] authors presented results they had obtained when testing cylindrical pressure vessels subjected to different load types. Based on performed analyses, formulas for calculating stresses on cylindrical shells were obtained, and results were verified by using experimental method

involving strain gauges. Determination of pressure values causing structures to plastically deform was presented in papers [6,7]. Failures of structures usually happen because of cracks appearing on locations with the greatest stress concentration, which was also verified in papers [8 - 10]. In the area with the greatest stress concentration, a crack initiates and later propagates. By using finite element method, authors obtained pressure value leading to initial plastic deformation, which was verified experimentally; at a later stage, by increasing pressure, they also obtained critical value leading to failure [9,10]. Valve housing was analysed as an example of complex geometry in papers [11,12]. In their paper [11], Mitrovic et al. analysed valve subjected to different load types. Assumptions from this numerical model complied well with results obtained by using experimental method – in elasticity area. Determination of pressure value causing valve housing to plastically deform, fail or be instable while subjected to internal pressure was presented in paper [12]. Since the plastic deformation does not occur under nominal pressure required by standard, authors used dimensions of valves and certain characteristic cross-sections and numerical analysis in order to obtain

Received:, October 2017, Accepted: December 2017

Correspondence to: Tasko Maneski
Faculty of Mechanical Engineering,
Kraljice Marije 16, 11120 Belgrade 35, Serbia
E-mail: tmaneski@mas.bg.ac.rs

doi:10.5937/fmet1802218M

© Faculty of Mechanical Engineering, Belgrade. All rights reserved

FME Transactions (2018) 46, 218-223 218

minimum pressure value causing valve to plastically deform. Testing of bends used in control system of A6 generator in Hydropower Plant Đerdap I Kladovo was presented in paper [13]. Besides, determination of plastic loads of cracked forged piping branch junctions under internal pressure and bending moment was presented in papers [14, 15]. Review of all experimental techniques applied in the field of pipeline integrity is shown in paper [16]. Analytical method for calculation of stress components for cylindrical shell with nozzles is shown in paper [17].

The subject of this paper is the analysis of a pipe branch model of A6 third pipeline at Hydropower Plant Perućica that is subjected to internal pressure. Experimental method with strain gauges was used for measuring stresses and determining locations with the greatest stress concentration. During FEM analysis, boundary conditions were set to be the same as in experiment, in order to compare results and verify numerical model. The model was subjected to internal pressure load that was gradually increased and internal pressure value causing pipe branch model to plastically deform was determined.

2. BASIC MODEL

Each structure of the vessel has perceivable locations with geometrical discontinuities where stress concentration is expected to occur. Therefore, an idea was to make a model of the given structure that would go through experimental procedure causing model to plastically deform since this was not possible to do on the real structure.

In the very beginning of model creation, it was necessary to solve the following question – what would be the appropriate relation of the pipe branch model dimensions and thickness compared to the real structure dimensions and thickness in order to realistically represent behaviour of the real structure?

As far as the model thickness and dimensions were concerned, starting formula for calculating stresses on

cylindrical shells (away from stiffeners and holes) was the one defined by pressure vessel standards (boiler formula).

The pipe branch model should give the same stress values as the real pipe branch and this is ensured by using similarity method (based on boiler formula) in the following way:

$$\sigma = \left(\frac{p \cdot R}{e} \right)_{real} = \left(\frac{\frac{p}{2} \cdot \frac{R}{5}}{\frac{e}{10}} \right) = \frac{p^{model} \cdot R^{model}}{e^{model}} \quad (1)$$

where p is internal pressure, R is radius of the vessel, e is thickness.

So, the pipe branch model was created with following features:

- dimensions of the model were 5 times smaller than of the real pipe branch;
- thickness: 36 mm was replaced with 4 mm (since there was no metal sheet with 3.6 mm thickness), which was the reason why obtained stress was 10% smaller than needed, 50 mm was replaced with 5 mm and 80 mm was replaced with 8 mm;
- the pipe branch model was made of steel S355J2+N (yield point in tension 355 MPa) since Nioval47 (yield point in tension 470 MPa), used for making of the pipe branch, was not available.

All of this was taken into account later, at the time of mapping results obtained on the model onto the real pipe branch structure.

3. EXPERIMENTAL ANALYSIS

Experimental measurements were taken at the Laboratory for Strength of Materials at the Faculty of Mechanical Engineering in Belgrade. Strain gauges were placed on characteristic locations imposed by the model geometry. Fig. 1 shows measurement locations where stress was measured with strain gauges. For the purpose of this testing, eight strain gauges were used, as well as data acquisition system of National Instruments (NI), USA.



Figure 1. Measuring locations MM1 – MM8

Figures 2 – 6 show pressure-related results of measurements taken with strain gauges on all measurement locations.

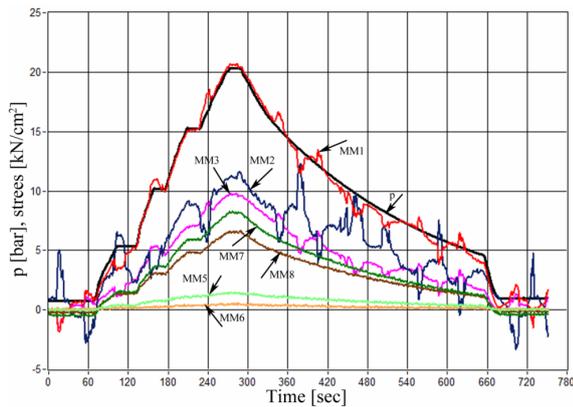


Figure 2. Measured stress as a function of pressure, for pressure values lower than 20 bar

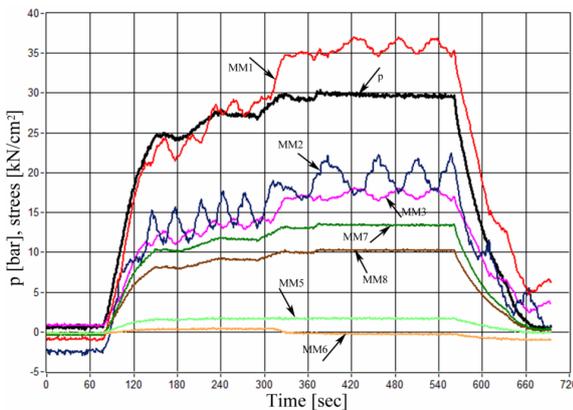


Figure 3. Measured stress as a function of pressure, for pressure value of 30 bar (plastic deformation occurs at MM1)

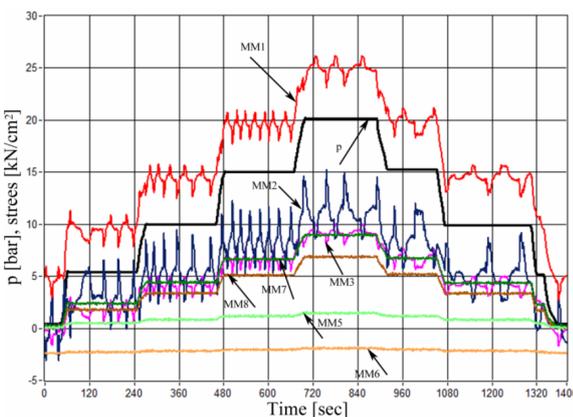


Figure 4. Measured stress as a function of pressure, after material at MM1 was plastically deformed (repeated 20 bar load, new plastic deformation does not occur)

Results of measurements are shown in Figures 2 – 6. The pipe branch model was subjected to 20 bar load several times. One of the results is shown in Fig. 2, where it is clear that the model material is in elasticity area. Then, the model was subjected to 30 bar pressure load, and Fig. 3 shows that plastic deformation occurred at the MM1 measuring location when subjected to this pressure. Afterwards, 20 bar testing was repeated, and it can be seen that new plastic deformation does not occur

(Fig. 4). Figure 5 shows, under 33 bar load, new plastic deformation occurred at the same MM1 measuring location. Further increase of load resulted in new plastic deformation at MM1 location occurred, but 37 bar pressure load also resulted in plastic deformation at MM2 measuring location, which is shown in Fig. 6. Plastic deformation did not occur at any other measuring locations; because of this, for further analysis, only MM1, MM2 and MM3 will be considered. These measuring locations are as follows: MM1 – circumferential direction of the cylinder with larger diameter, MM2 – vertical direction on the stiffener, on the side of the conical section of the model and MM3 – circumferential direction on the conical section of the model.

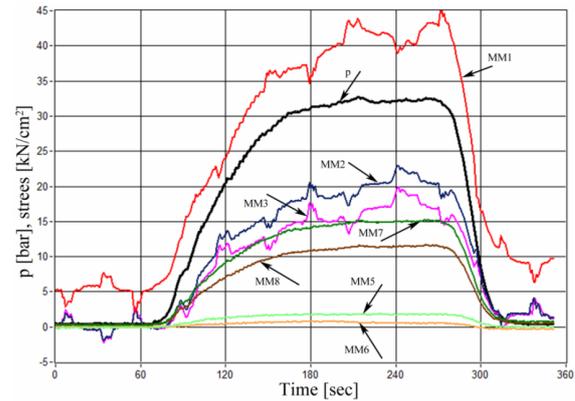


Figure 5. Measured stress as a function of pressure, after material at MM1 was plastically deformed (33 bar load, new plastic deformation occurs at MM1)

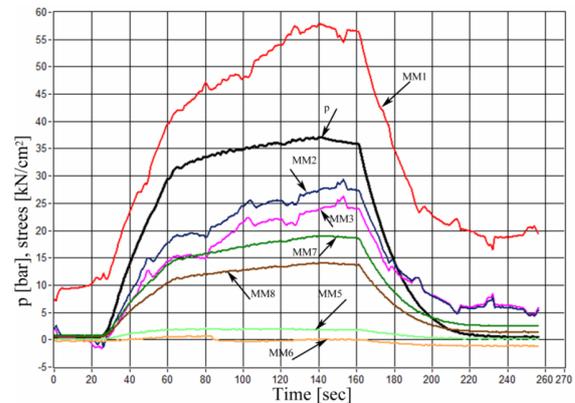


Figure 6. Measured stress as a function of pressure, for pressure value of 37 bar (new plastic deformation occurs at MM1 location and plastic deformation occurs at MM2 location)

4. FINITE ELEMENT METHOD ANALYSIS

For the purpose of strength analysis by using finite element method, a 3D model of the pipe branch was created. Figure 7 shows model geometry. Numerical model of the pipe branch was subjected to 20 bar internal pressure.

Figure 8 shows circumferential stresses of the pipe branch model at critical locations. Since this was a linear analysis of the structure (obtained stress had linear nature related to set pressure), it was possible to use scaling for obtaining results for other internal pressure values.

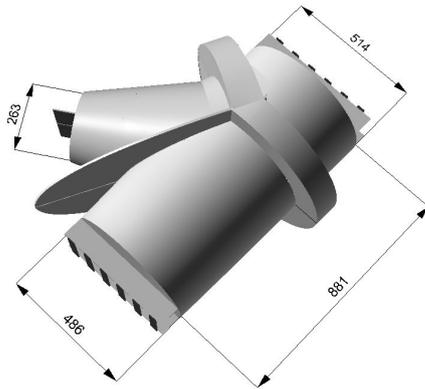


Figure 7. Geometry of the pipe branch model

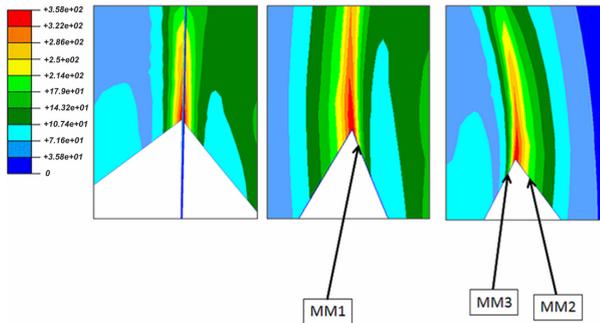


Figure 8. Stresses [MPa] in circumferential (vertical) direction at MM1, MM2 and MM3 measuring locations (p = 20 bar)

5. COMPARISON OF RESULTS OBTAINED BY EXPERIMENTAL AND NUMERICAL ANALYSIS (ELASTICITY AREA)

After analysis of obtained results, it was concluded that the greatest stress values appeared in MM1 circumferential direction, as well as at MM2 and MM3 measuring locations. Stress values at other measuring locations can be neglected since they were considerably lower than the yield point of the given material. Table 1 shows results of stress measurements taken with strain gauges and results obtained by using finite element method for 20 bar pressure.

Table 1. Comparison of results obtained by experimental measurement and numerical calculation

	Stress [MPa]	
	Measurements (strain gauges)	FEM
MM1	220	230
MM2	120	162
MM3	98	116

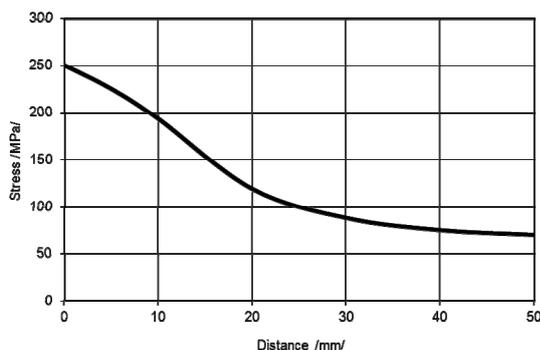


Figure 9. Stress distribution along the surface with distance 50 mm from critical zone at MM1

Stress distribution along the surface with distance 50 mm from critical zone (stress concentration area) at MM1 is shown in Fig. 9. General conclusion is that the values obtained by presented methods are very close, i.e. numerical finite element method verified experimentally obtained results.

6. DETERMINATION OF PLASTIC DEFORMATION AND MAPPING OF MODEL RESULTS ONTO THE REAL STRUCTURE

Figure 2 shows that all strain gauges returned to their initial states and that the pipe branch model was in elasticity area when subjected to 20 bar pressure. However, by viewing Fig. 3, it can be seen that plastic deformation of the pipe branch model occurred at MM1 location when subjected to 30 bar pressure. Figure 3 shows that stress line (strain gauge at MM1 location) did not return to 0 but to 5 kN/cm² (50 MPa) value, which is a clear indication that plastic deformation occurred at this location when pipe branch model was subjected to internal pressure of 30 bar. Then, the pipe branch was subjected to 20 bar again, and Figure 4 shows that new plastic deformation did not occur at MM1 location (strain gauge started growing from 5 kN/cm² and returned to 5 kN/cm²). Figure 5 shows a diagram when the model was subjected to 33 bar pressure and it can be seen that strain gauge at MM1 location started growing from 5 kN/cm² (50 MPa) but then returned to 10 kN/cm² (100 MPa) which indicates that new plastic deformation occurred at MM1. Under 37 bar (Fig. 6), plastic deformation occurred at MM1 location again, i.e. it can be seen that strain gauge at MM1 location started growing from 10 kN/cm² (100 MPa), but then returned to 20 kN/cm² (200 MPa). Also, under pressure of 37 bar, it can be seen that plastic deformation occurred at MM2 location as well.

If one gets back to similarity method, can be concluded that the pressure value causing real pipe branch A3 third pipeline at Hydropower Plant Perućica to plastically deform at MM1 location (location with the greatest stress) will be like this:

$$p = 30 \cdot 0.9 \cdot \frac{47}{35.5} \cdot 2 = 71.5 \text{ bar.} \quad (2)$$

Coefficient 0.9 is ratio between thickness of real pipe branch and of pipe branch model at MM1 location – 36mm/40mm.

Ratio 470/355 is the ratio between yield point in tension for real pipe branch material (NIOVAL47) and for pipe branch model material (St355J2+AR).

Coefficient 2 is coefficient of the model.

$$\text{Reliability coefficient for pipe branches is } 1.43 = \frac{71.5}{50}.$$

All previously mentioned means that real pipe branch should not be exposed to pressure higher than 50 bar.

Plastic deformation at other measuring locations will occur when pipe branch is subjected to much higher pressure values.

It was possible to apply similarity method to this pipe branch model subjected to internal pressure because all stresses were predominantly membrane stresses, with a very small contribution of bending stresses.

7. CONCLUSION

When it is not possible to directly test real vessel structures and when non-destructive methods do not give satisfactory results of behavioural prediction of the given structure during its exploitation (and in non-standard working conditions), one of the ways for solving the problem is creation of a model of that structure and its testing. For the purpose of this paper, subsized model of the pipe branch of A6 third pipeline at Hydropower Plant Perućica was made in order to be subjected to a detailed experimental testing. Numerical calculation was performed by using finite element method. Numerical pipe branch model was verified with experimental results (in elasticity area).

The main aim was to experimentally obtain internal pressure value causing pipe branch model to plastically deform. Obtained result was mapped onto the real pipe branch structure in order to obtain maximum calculated internal pressure value to which the structure may be subjected when in exploitation. Besides, weak spots on the structure were verified by obtaining same results through experiment and calculation, which gives good guidelines for monitoring of this structure during usage, since it is possible, by using this analysis, to decrease number of measurement locations for monitoring (in order to control exactly those measurement locations, which proved to be the most endangered).

REFERENCES

- [1] Živković, M., and Maneski, T.: Thermomechanical stresses of pipelines and vessels (Termomehanički naponi cevovoda i posuda), Monograph, Smeits, Beograd, 2006.
- [2] Gaćeša, B., Maneski, T., Vesna M.M.: Condition and Behavior Diagnostics of Boiler Constructions, FME Trans, Vol. 40, pp. 87-92, 2012.
- [3] Maneski, T.: Structure behavior analysis and diagnostics, FME Trans, Vol. 33, No. 2, pp. 89-95, 2005.
- [4] Petrović, A.: Stress analysis in cylindrical pressure vessels with loads applied to the free end of a nozzle, Int. J. Pres. Ves. Pip. Vol.78, pp.485-493, 2001.
- [5] Petrović, A., Balać, M., Jovović, A., and Dedic, A.: Oblique nozzle loaded by the torque moment – stress state in the cylindrical shells on the pressure vessel, Proc. Inst. Mech. Eng. C J. Mech. Eng. Sci. Vol. 226, pp. 567 – 575, 2012.
- [6] Patel, D.M., and Kumar, B., Limit load estimation of cylindrical vessel with oblique nozzle, IJERT Vol. 2, pp. 2421 – 2427, 2013.
- [7] Xuan, F.Z., Li, P.N., Tu, S.T.: Limit load analysis for the piping branch junctions under in – plane moment, Int.J.Mech.Sci. Vol.48, pp. 460-467, 2006.
- [8] Petrasinovic, N., Petrasinovic, D., Rasuo, B., Milkovic, D.: Aircraft Duraluminium Wing Spar Fatigue Testing, FME Transactions Vol. 45, pp. 531-536, 2017.
- [9] Sang, Z.F., Xue, L.P., Lin, Y.J., and Widera, G.E.O.: Limit and burst pressures for a cylindrical shell intersection with intermediate diameter ratio, Int. J. Pres. Ves. Pip, Vol. 79, pp. 341 – 349, 2002.
- [10] Chapuliot, S., Moulin, D. and Plancq, D., Mechanical behavior of a branch pipe subjected to out-of-plane bending load, J. Press. Vess. T, Vol. 124, No. 1, pp. 7 – 13, 2002.
- [11] Galić, I., Vučković, K., and Tonković, Z.: Nonlinear analysis of two – way globe valve housing, Tehn. vjesn, Vol. 17, pp. 67-74, 2010.
- [12] Mitrović, N., Milošević, M., Momčilović, N., Petrovic, A., Sedmak, A., Maneski, T., and Zrilic, M.: Experimental and numerical analysis of local mechanical properties of globe valve housing, Chem. Listy, Vol. 106, pp. 491 – 494, 2012.
- [13] Dinić, I., Arsić, M., Međo, B., Stefanović, A., Grabulov, V., and Rakin, M.: Effect of welded joints imperfection on the integrity of pipe elbows subjected to internal pressure, Tehn. Vjesn, Vol. 20, pp. 285-290, 2013.
- [14] Yahiaoui, K., Moffat, D.G., and Moreton, D.N.: The collapse behaviour of a forged piping branch junction under internal pressure, Proc 9th International Conference Pressure Vessel Technology, Sydney, (2000).
- [15] Yahiaoui, K., Moffat, D.G., and Moreton, D.N., Plastic loads of cracked forged piping branch junctions: experimental results and comparison with numerical data, Int. J. Pres. Ves. Pip, Vol. 77, pp. 249-260, 2000.
- [16] Freire, J.L.F., Vieira, R.D., Benjamin, A.C., Experimental techniques in the field of pipeline integrity, Exp. Techniques, Vol. 30, No. 4, pp. 44-50, 2006.
- [17] Ming-De Xue, Qing-Hai Du, Keh-Chih Hwang and Zhi-Hai Xiang: An analytical method for cylindrical shells with nozzles due to internal pressure and external loads – part I: theoretical foundation, J. Press. Vess.T. Vol. 132, No.3, pp. 031206-1 – 031206-9, 2010.

ОДРЕЂИВАЊЕ ВРЕДНОСТИ УНУТРАШЊЕГ ПРТИСКА КОЈИ ЋЕ ДОВЕСТИ ДО ПЛАСТИЧНЕ ДЕФОРМАЦИЈЕ НА МОДЕЛУ РАЧВЕ

**Т. Манески, Д. Бајић, Н. Момчиловић,
В. Милошевић Митић, М. Балаћ**

Сложеност геометрије посуда под притиском обично представља узрок појаве концентрације напона и деформација. Савремени приступ анализе стања напона и деформација укључује нумеричка и експериментална испитивања. Свако експериментално тестирање на реалној конструкцији може угрозити саму конструкцију. Стога, прављење модела неке конструкције има велике предности. Умањени модел рачве А6 трећег цевовода на ХЕ Перућица, Никшић је израђен како би био подвргнут детаљном експерименталном тестирању. Циљ је био да се одреди вредност унутрашњег притиска који доводи до пластичне деформације на

моделу рачве и да се ови резултати користе за одређивање притиска који ће стварну конструкцију довести до пластичног деформисања без икаквих мерења на самој конструкцији. Експериментална мерења су спроведена методом мерних трака. Мерне траке су позициониране на критичне зоне. Нумерички модел и резултати добијени методом коначних елемената (ФЕМ) потврђени су експерименталним резултатима (у области еластичности). Након верификације у еластичној области, повећањем притиска, експериментално одређена је критична вредност унутрашњег притиска који је изазвао пластичну деформацију модела рачве. На основу

понашања модела рачве и након одређивања односа између модела и стварне конструкције, процењује се максимална израчуната вредност унутрашњег притиска на коју се реална конструкција може изложити. Поред тога, слабе тачке на конструкцији су потврђене добијањем истих резултата кроз експеримент и прорачун, што даје добре смернице за праћење ове конструкције током експлоатације, с обзиром на то да је оваквом анализом могуће смањити број мерних места за праћење (у смислу да се контролишу тачно она мерна места која су се показала као најкритичнија).

- [Support](#)
- [Training](#)
- [Contact Us](#)
- [clarivate.com](#)

[Master Journal List](#)

Site

Client

proxystylesheet

Output

Search 

allAreas

Journal Search

Emerging Sources Citation Index - JOURNAL LIST

[A](#) [B](#) [C](#) [D](#) [E](#) [F](#) [G](#) [H](#) [I](#) [J](#) [K](#) [L](#) [M](#) [N](#) [O](#) [P](#) [Q](#) [R](#) [S](#) [T](#) [U](#) [V](#) [W](#) [X](#) [Y](#) [Z](#)

Total journals: **160** · "F" Journals 61-70 (of 160)



Format for print A-Z

- **FME TRANSACTIONS**

Quarterly ISSN: 1451-2092

UNIV BELGRADE, FAC MECHANICAL ENGINEERING, KRALJICE MARIJE 16, 35, BELGRADE, SERBIA, 11120

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **FOCAAL-JOURNAL OF GLOBAL AND HISTORICAL ANTHROPOLOGY**

Semiannual ISSN: 0920-1297

BERGHAHN JOURNALS, 20 JAY ST, SUITE 512, BROOKLYN, USA, NY, 11201

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **FOCUS ON HEALTH PROFESSIONAL EDUCATION-A MULTIDISCIPLINARY JOURNAL**

Tri-annual ISSN: 1442-1100

AUSTRALIAN NZ ASSOC HEALTH PROFESSIONAL EDUCATORS-ANZAHPE, C/HEALTH PROFESSIONAL EDUCATION, FLINDERS UNIV, PO BOX 852, RENMARK, AUSTRALIA, SA 5341

[Coverage](#)

- [Emerging Sources Citation Index](#)

- **FOLIA LINGUISTICA ET LITTERARIA**


Semiannual ISSN: 1800-8542

UNIV MONTENEGRO, INST LANGUAGE & LITERATURE, FAC PHILOSOPHY-NIKSIC, DANILA

Sources

CiteScore metrics for serials

CiteScore metrics from Scopus are comprehensive, transparent, current and free metrics for serial titles in Scopus. Search or browse below to find a source and see associated metrics. Use the annual metrics for reporting, and track the progress of 2017 metrics with CiteScore Tracker 2017. Be sure to use qualitative as well as the below quantitative inputs when presenting your research impact, and always use more than one metric for the quantitative part.

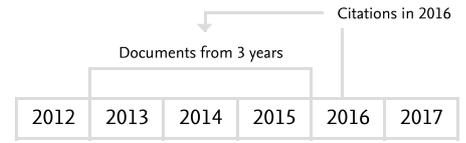

Search for a source

Browse sources

Download Scopus Source List

Search 1451-2092

○ Title ○ ISSN ○ Publisher Display only Open Access journals

1 source found matching "1451-2092".

Clear filters

Source title	CiteScore	SJR	SNIP	Type
FME Transactions Open Access	0.59	0.205	0.550	Journal

Top of page

About Scopus

- What is Scopus
- Content coverage
- Scopus blog
- Scopus API
- Privacy matters

Language

- 日本語に切り替える
- 切换到简体中文
- 切换到繁体中文
- Русский язык

Customer Service

- Help
- Contact us

ELSEVIER

Terms and conditions Privacy policy

Copyright © 2018 Elsevier B.V. All rights reserved. Scopus® is a registered trademark of Elsevier B.V.

Cookies are set by this site. To decline them or learn more, visit our Cookies page.

RELX Group™

Source details

FME Transactions

Open Access ⓘ

Scopus coverage years: from 2011 to 2017

Publisher: Faculty of Mechanical Engineering, Belgrade University

ISSN: 1451-2092

Subject area: [Engineering: Mechanical Engineering](#) [Engineering: Mechanics of Materials](#)

[View all documents >](#) [Set document alert](#) [Journal Homepage](#)

[Visit Scopus Journal Metrics ↗](#)

CiteScore 2016 ⓘ
0.59

SJR 2016 ⓘ
0.205

SNIP 2016 ⓘ
0.550

[CiteScore](#) [CiteScore rank & trend](#) [Scopus content coverage](#)

CiteScore **2016** ▼ Calculated using data from **31 May, 2017**

$$0.59 = \frac{\text{Citation Count 2016}}{\text{Documents 2013 - 2015}^*} = \frac{89 \text{ Citations } >}{150 \text{ Documents } >}$$

*CiteScore includes all available document types [View CiteScore methodology >](#) [CiteScore FAQ >](#)

CiteScoreTracker 2017 ⓘ Last updated on *06 March, 2018*
Updated monthly

$$0.91 = \frac{\text{Citation Count 2017}}{\text{Documents 2014 - 2016}} = \frac{148 \text{ Citations to date } >}{163 \text{ Documents to date } >}$$

CiteScore rank ⓘ

Category	Rank	Percentile
Engineering		
└ Mechanical Engineering	#316/526	39th
Engineering		
└ Mechanics of Materials	#198/323	37th

[View CiteScore trends >](#)
[Add CiteScore to your site ↗](#)

Metrics displaying this icon are compiled according to Snowball Metrics ↗, a collaboration between industry and academia.

About Scopus

- [What is Scopus](#)
- [Content coverage](#)
- [Scopus blog](#)
- [Scopus API](#)
- [Privacy matters](#)

Language

- [日本語に切り替える](#)
- [切换到简体中文](#)
- [切换到繁體中文](#)
- [Русский язык](#)

Customer Service

- [Help](#)
- [Contact us](#)

Link Rada:

<http://www.mas.bg.ac.rs/istrazivanje/fme/start>

http://www.mas.bg.ac.rs/_media/istrazivanje/fme/vol46/2/10_m_balac_et_al.pdf